arXiv:cond-mat/0610450v1 [cond-mat.mtrl-sci] 17 Oct 2006

Unconventional relaxation in antiferromagnetic $CoRh_2O_4$ nanoparticles

R.N. Bhowmik* and R. Ranganathan†
Experimental Condensed Matter Physics Division,
Saha Institute of Nuclear Physics, 1/AF, Bidhannagar, Calcutta 700064, India

Magnetic relaxation in antiferromagnetic $CoRh_2O_4$ nanoparticles is investigated at 2 K by cooling the sample from a temperature (70 K) well above the antiferromagnetic ordering temperature at 27 K, following zero field cooled (ZFC) and field cooled (FC) process. In ZFC process, the sample at 2 K is subsequently followed by magnetic field on and off sequences, whereas in FC process the cooling field is made off during measurement of remanent magnetization as a function of time. The experiments suggest an unconventional relaxation behaviour in the system, as an effect of increasing surface exchange anisotropy with decreasing the size of antiferromagnetic nanoparticles.

Spinel oxides belong to a special class of materials with formula unit AB_2O_4 [1], where cations are occupied in A (tetrahedral) and B (octahedral) sublattices, respectively. Recently, many unusual and interesting phenomena like magnetic quantum tunneling and superparamagnetism [2] have been observed in spinel nanoparticles. These phenomena, owing to their tremendous applications in nanoscience and technology, are drawing increasing attention to the research community. The other notable phenomenon under current interest is the geometrical frustration effect. The change of degeneracy and topology of the antiferromagnetic ground state (Neel order) of a geometrically frustrated system has shown various kinds of non-conventional magnetic ordering [3, 4, 5, 6]. One such phenomenon is quantum spin fluctuation effect, where the spins do not order and remain in a "collective paramagnetic state" down to zero temperature. Some of the spinel oxides due to their typical lattice structure have shown geometrical frustration effect [7, 8]. Geometrical frustration effect has been observed in those antiferromagnetic spinels where magnetic moments are occupied either in B or in A sublattice. For example, $ZnFe_2O_4$ is a spinel compound(structure: $(Zn^{2+})_A[Fe_2^{3+}]_BO_4)$ where magnetic ions (Fe^{3+}) are confined in the B sublattice alone. On the other hand, $CoRh_2O_4$ is another spinel (structure: $(Co^{2+})_A[Rh_2^{3+}]_BO_4)$ where magnetic ions (Co^{2+}) are confined in the A sublattice alone. Note that A-O-A (intra A sublattice) superexchange interactions are generally believed to be smaller in comparison with B-O-B (intra B sublattice) superexchange interactions. However, $CoRh_2O_4$ (A-O-A) and $ZnFe_2O_4$ (B-O-B) both are antiferromagnet, and $T_N \approx 27$ K of $CoRh_2O_4$ is larger than $T_N \approx 10$ K of $ZnFe_2O_4$ [1]. In view of the earlier experimental results [9], we believed that $CoRh_2O_4$ can provide an alternative antiferromagnetic spinel for studying the geometrical frustration effect. We have seen that cubic spinel structure as well as antiferromagnetic ordering temperature at 27 K of the bulk sample are also retained in the $CoRh_2O_4$ nanoparticles. The unalternation of T_N excludes the possibility of site exchange between A sublattice (Co^{2+}) and B sublattice (Rh^{3+}) ions in $CoRh_2O_4$ nanoparticles. The nanoparticles of $CoRh_2O_4$ (size down to 16 nm) were obtained by mechanical milling of bulk sample. Mechanical milling is one of the most convenient methods which can controll the surface spin ordering by contributing some strain induced anisotropy [10]. The dc magnetization (M) as a function of time (t), temperature (T) and field (H) were measured using SQUID (Quantum Design, USA) magnetometer. Before loading each sample in SQUID magnetometer, zero field was checked by measuring the field dependence of magnetization of a paramagnetic sample at 35 K.

We have analysed the zero field cooled magnetization [MZFC (T)] data above 50 K using Curie-Weiss law: $\chi = \frac{C}{T-\theta_A}$, where C and θ_N have the usual meaning [9]. The analysis showed that effective paramagnetic moment (μ_{eff}= $(3kC/N)^{1/2}$, where k is the Boltzman constant, N is the number of $CoRh_2O_4$ formula unit per gm of the sample) of the system increases with the decrease of particle size. We also noted that μ_{eff} of the bulk sample is large compared to $\mu_{eff} \sim 4.60\ \mu_B$ for the Co^{2+} moment alone. Such an increase in Co-Rh compound could be the effect of the spin-orbital coupling of 3d(Co)-4d(Rh) elements [11]. It is found that the ratio of θ_A/T_N is always greater than 1 for nanoparticles. This is a good indication of geometrical frustration effect in $CoRh_2O_4$ nanoparticles, as well as the increasing instability of antiferromagnetic ordering [12] in surface spin configurations. It is noted that the initial increase of θ_A/T_N (-44.23 K/27 K for bulk, -42.80 K/27 K for 70 nm, -42.05 K/27 K for 50 nm, -41.84 K/27 K for 32 nm, -43.81 K/27 K for 19 nm and -51 K/27 K for 16 nm) with decreasing the particle size down to 36 nm is followed by the decrease on further lowering the particle size. This suggests that magnetic instability is not monotonous with decreasing the particle size of the present antiferromagnetic spinel. A better magnetic ordering, which is different from the typical antiferromagnetic order, can be observed for smaller particles. The magnetic instability in the nanoparticle samples is also reflected by the

---

*Corresponding author(RNB):
e-mail: rabindranath.bhowmik@saha.ac.in
Present address: Department of Physics, Pondicherry University, R.V. Nagar, Kalapet, Pondicherry-605014
†e-mail (RR): r.ranganathan@saha.ac.in

observation of magnetic irreversibility between the temperature dependence of zero field cooled magnetization (MZFC) and field cooled magnetization (MFC) below T_N, whereas the increasing magnetic order with decreasing the particle size is confirmed from the M(H) data. Such observation is also consistent with the prediction of disorder induced magnetic order in geometric frustrated system [6] or induced ferromagnetism in antiferromagnetic nanoparticle [13]. The other notable feature consistent with disorder induced magnetic order is that magnetization below T_N had shown a systematic enhancement with decreasing the particle size. A scaling analysis suggested that such an increase of low temperature magnetization is a consequence of superparamagnetism (collective paramagnetism), arising from the increasing number of frustrated surface (shell) spins in nanoparticles. The small irreversibility between FC and ZFC magnetization (MFC > MZFC) below T_N suggests that a fraction of surface spins might be in blocking state and field cooling gives better magnetic ordering of those blocked surface spins. However, we do not find any ferromagnetic hysteresis loop in our nanoparticles, unlike other class of antiferromagnetic (AFMNP) nanoparticles [14, 15, 16, 17] that showed exchange bias effect and the hysteresis loop like ferromagnetic materials. These unusual phenomena in AFMNP are the indication of strong inter-particle interactions, which has been reflected in the blocking behaviour of nanoparticles below a characteristic temperature, known as average superparamagnetic blocking temperature (T_B) of the nanoparticle sample. In such cases, the superparamagnetc behaviour is characterized by the shift of T_B with applied magnetic field in zero field cooled dc magnetization or with applied frequency in ac susceptibility measurements. Since the blocking temperature, associated with a peak in zero field cooled magnetization, is not observed in our AFMNP down to 2 K, an alternative approach is essential for the understanding of surface superparamagnetism in antiferromagnetic nanoparticles, like we are having.

The present work has probed the relaxation experiments to understand the magnetic instability, essentially related to the surface spin dynamics, in $CoRh_2O_4$ nanoparticles. The understanding could be relevant to clarify certain issues like surface spin configuration, competitive effect between the shell (surface) and core spins in antiferromagnetic nanoparticles. In the relaxation experiments, samples are zero field cooled from 100 K to the measurement temperature (T_m) at 2 K. After cooling, the samples are equilibrated at 2 K in the absence of external magnetic field for the waiting time (t_w) $\sim$ 100 seconds. Then external magnetic field (H) = 100 Oe is applied, which is stabilized within 60 seconds. The time dependence of the magnetization is recorded for the next (t_{on}) 2700 seconds (definded as ON state). Then magnetic field is switched off and the magnetic field is stabilised to zero value within 60 seconds. However, the measurement of M(t) is continued for the next (t_{off}) 2700 seconds in the absence of magnetic field (defined as OFF state). We have shown the experimental data for two selected nanoparticle samples in Fig. 1. The M(t) data during ON state and OFF state are also separately shown for all the samples in Fig. 2 and Fig. 3a, respectively. It is worthy to mention that relaxation behaviour is not observed for bulk sample. This is consistent with the long range antiferromagnetic order of the sample. On the other hand, relaxation behaviour is observed in all nanoparticle samples. We have noted a cross over in the magnetic relaxation behaviour depending on the size of particles. The experimental data show an unusual decrease of magnetization with the increase of time, *i.e. negative magnetization growth with time*, during the field ON state for samples with particle size down to $\sim$ 19 nm. Such magnetic relaxation behaviour in the presence of magnetic field is unusual in view of the conventional domain growth, specially applicable for spin glass or superparamagnetic systems. On further lowering the particle size, the system shows the as usual increase of magnetization with time in the presence of magnetic field, *i.e. positive magnetization growth with time* (as seen for sample with particle size $\sim$ 16 nm). Now, look at the M(t) data during field OFF state of the measurement. Fig. 3a shows that the isothermal remanent magnetization M(t) during OFF state decreases with the increase of time. Interestingly, that decrease is becoming slower with time for the smaller particles. We have understood such a slow decrease of M(t) during OFF state by comparing it with the convensional time decay of field cooled remanent magnetization for 16 nm sample. The time dependence of remanent magnetization at 2 K is preceeded by 100 Oe field cooling from 70 K to 2 K (rate 5 K/minute) and subsequently, waited there for 100 seconds before reducing the field to zero value and starts the recording. The remanent magnetization M(t) data is normalized by the first point M(i) during OFF state, where i = 10 sec. and 2800 sec. for FC and ZFC process (during first 2700 sec. field is ON), respectively. The normalized M(t)/M(i) data are shown in Fig. 3b. We have seen that M(i) $\sim$ 9.9×10^{-4} emu/g for FC-OFF is larger than M(i) $\sim 2.0 \times 10^{-4}$ emu/g for ZFC-OFF process, and the magnitude of M(t) is larger throughout the time (0-2800 seconds) after switing off the cooling field in FC process in comparison with the OFF state (2800-5500 seconds) in ZFC process. Fig. 3b shows that the rate of decay of remanent magnetization is more slower in FC process than that of the OFF state in ZFC process. One would expect the establishment of a metastable magnetic order in the surface spin configurations during the field cooling process from 70 K (> T_N $\sim$ 27 K) down to 2 K. The increase of interaction networks among the surface spins can give rise a larger field cooled remanent magnetization, whereas the rate of decay of remanent magnetization is related to the strength of interactions among the spins, resulting in a slower decay for increasing interactions.

Most of the reports explained the superparamagnetic behaviour in nanoparticle system by assuming the spin flips between spin up ($\theta_0 = 0^0$) and spin down ($\theta_0 =$

180^0) states, taking into account the anisotropy barrier E = - KVcos^2 θ_0 [16]. This may not be a realistic model for nanoparticle system, also pointed out by other group [18]. One would expect a distribution of canting angle (θ) between surface spin configurations. Consequently, we can expect a distribution of energy minima as a function of spin canting angle ($0^0 < \theta < 180^0$). The spin can relax in any one of the modified energy minima, determined by local configurations. The observed magnetic relaxation of $CoRh_2O_4$ nanoparticles can be explained by the core-shell model [9], which we proposed by taking into account the variation of surface spin canting angle with particle size. We have considered that interaction between core spins are antiferromagnetic, whereas interaction between core-shell spins are distorted antiferromagnetic. On the otherhand, interaction between shell spins are effectively superparamagnetic. When the particle size is reduced, some of the A-O-A superexchange bonds become frustrated. These frustrated bonds will create exchange anisotropy field at the interfacial surface. The decrease of magnetization with time in the presence of constant magnetic field suggests a competition between AFM exchange interactions of core (bulk) and surface anisotropy field (unidirectional) at the surface spins. The competitive effect of the interactions is explained with the help of a schematic diagram (Fig. 4). For spin vectors, the effective magnetic field (along + z axis) $H_{eff} = H_{ex} + H_{san} + H_{appl} + \Delta$, where H_{ex} is the Heisenberg exchange interactions field (negative for antiferromagnetic ordering), H_{san} is the surface exchange anisotropy field, H_{appl} is the applied external field, and Δ is small contribution from other sources. For typical bulk AFM, $H_{san} = 0$, $H_{ex} >> H_{appl}$ (100 Oe in the present experiment), and perfect AFM ordering compensates the magnetization vectors (Fig. 4a). The distortion of AFM order in nanoparticle favours canting between shell spins. The canting ($0^0 < \theta < 180^0$) between two nearest neighbour spins gives rise the resultant magnetization vector (μ), which makes angle ϕ ($0 < \phi < 90^0$) with the z direction (Fig. 4b). The magnetization (M) is the effective component of (μ) along +z direction, *i.e.* M = μ_z. Remember that resultant surface exchange anisotropy field may not be along the + z axis. We have assumed that H_{san} is the effective component of surface exchange anisotropy field along + z axis. The effect of H_{san} is to increase the surface magnetization [19, 20] by decreasing ϕ, whereas H_{ex} tries to compensate magnetization vectors ($\mu = 0$). This establishes a non-equilibrium local magnetic ordeing of the surface spins, before attaining an equilibrium magnetic state M_{eq} (H,T,t). The effective magnetization M(T) of (larger size) nanoparticle at a constatnt temperature below T_N may be larger, due to the contributions from H_{san}, than the corresponding bulk sample. At the same time, there is also a finite probability for the shell spins of nanoparticle, under temperature and field equilibrium for a longer observation time, of restoring the bulk M(T) state, if the surface spin configuration of nanoparticle sample does not drastically differ from the bulk (180^0) configuration [14]. The time evolution of the local non-equilibrium magnetization may not have any significant effect, because of the very small magnitude, on the observed value of thermal activated magnetization at constant external magnetic field (100 Oe). However, such time evolution (relaxation dynamics of shell spin configurations) can effectively show the decrease of magnetization even in the presence of external magnetic field, as long as $H_{ex} >> H_{san}$. Now, consider the case where H_{san} begins to dominate over H_{ex} for antiferromagnetic nanoparticles below a critical size (Fig. 4c). Here, antiferromagnetic field H_{ex} is effectively reduced in magnitude (schematically shown in Fig. 4 in Ref. [9] and the effect is already found in many antiferromagnetic nanoparticles [14, 15, 16, 17]). The effective decrease of antiferromagnetic exchange interactions results in the further decrease of ϕ for smaller particles. Consequently, the probability of restoring the bulk M(T) state becomes less. On the other hand, the local magnetic ordering of the shell spins in the presence of external magnetic field favours the establishment of a new metastable state where M(T) data increases with the increase of time.

In summary, Bulk (core) magnetization is a stable antiferromagnetic state, whereas magnetization of nanoparticles can be considered as an distorted antiferromagnetic state. At thermal equilibrium the core spins of nanoparticles will try to align the neighbouring shell spins in antiferromagnetic manner, which results in a finite probability of decreasing the surface magnetization with time. On the other hand, surface anisotropy field will try to give rise a preferential induced magnetic ordering to the shell spins, which results in the increase of surface magnetization with time. When the particle size is large (i.e. surface anisotropy field is small), there is a greater probability for the nanoparticle sample of restoring the equilibrium magnetization M_{eq} of bulk sample at that temperature. On decreasing the particle size, such probability of restoring the bulk magnetic state becomes less, and the sample is locally ordered to a metastable state where magnetization increases with time. This demonstrate the evidence of an unconventional relaxation process in the system. The experimental results also provided an alternative approach to identify qualitatively the increasing surface exchange anisotropy with decreasing the size of antiferromagnetic nanoparticle.

---

[1] V. A. M. Brabers, Hand book of Magnetic Materials, edited by K. H. Buschow **8**, 189 (1995)

[2] J. Tejada, R. F. Ziolo and X. X. Zhang, Chem. Mater. **8**, 1784 (1996)

[3] M.E. Zhitomirosky, A. Honecker and O.A. Petrenko, Phys. Rev. Lett. **85**, 3269 (2000)

[4] J. Villain, Z. Phys. B **33**, 31 (1978)

[5] C. L. Henley, Phys. Rev. Lett. **62**, 2056 (1989)

[6] H. Reichert, V.N. Bugaev, O. Shchyglo, A. Schöps, Y. Sikula and H. Dosch, Phys. Rev. Lett. **87**, 236105 (2001)

[7] N. Tristan, J. Hemberger, A. Krimmel, H-A. Krug von Nidda, V. Tsurkan, and A. Loidl, Phys. Rev. B **72**, 174404 (2005)

[8] H. Ueda, H.A. Katori, H. Mitamura, T. Goto, and H. Takagi, Phys. Rev. Lett. **94**, 047202 (2005)

[9] R.N.Bhowmik, R. Nagarajan and R. Ranganathan, Phys. Rev. B **69**, 054430 (2004)

[10] R.N. Bhowmik, R. Ranganathan, R. Nagarajan, Biswatosh Ghosh, and S. Kumar, Phys. Rev. B **72**, 094405 (2005)

[11] D. Zitoun, M. Respaud, M. Fromen, M.J. Casanove, P. Lecante, C. Amiens, and B. Chaudret, Phys. Rev. Lett. **89**, 037203 (2002)

[12] S.E. palmer and J.T. Chalker, Phys. Rev. B **62**, 488 (2000)

[13] L. Neel, in Low Temperature Physics, edited by C. Dewitt, B. Drefus, and P.D. de Gennes (Gordon and Beach, New York, 1962), p. 413

[14] J. Tejada, X. X. Zhang, E. del Barco, J. M. Hernandez, and E. M. Chudnovsky, Phys. Rev. Lett. **79**, 1754 (1997)

[15] S.A. Makhlouf, F.T. Parker, S. Spada, and A.E. Berkowitz, J. Appl. Phys. **81**, 5561 (1997)

[16] E. del Barco, M. Duran, J.M. Hernandez, J. Tejada, R.D. Zysler, M.V. Mansilla, and D. Fiorani, Phys. Rev. B **65**, 052404 (2002)

[17] J.van Lierop, H.S. Isaacs, D.H. Ryan, A. Beath, and E. McCalla, Phys. Rev. B **67**, 134430 (2003)

[18] J.D. Lee, Phys. Rev. B **70**, 174450 (2004)

[19] K. Takano, R. H. Kodama, A. E. Berkowitz, W. Cao and G. Thomas, Phys. Rev. Lett. **79**, 1130 (1997)

[20] O. Iglesias, X. Battle, and A. Labarta, Phys. Rev. B **72**, 212401 (2005)

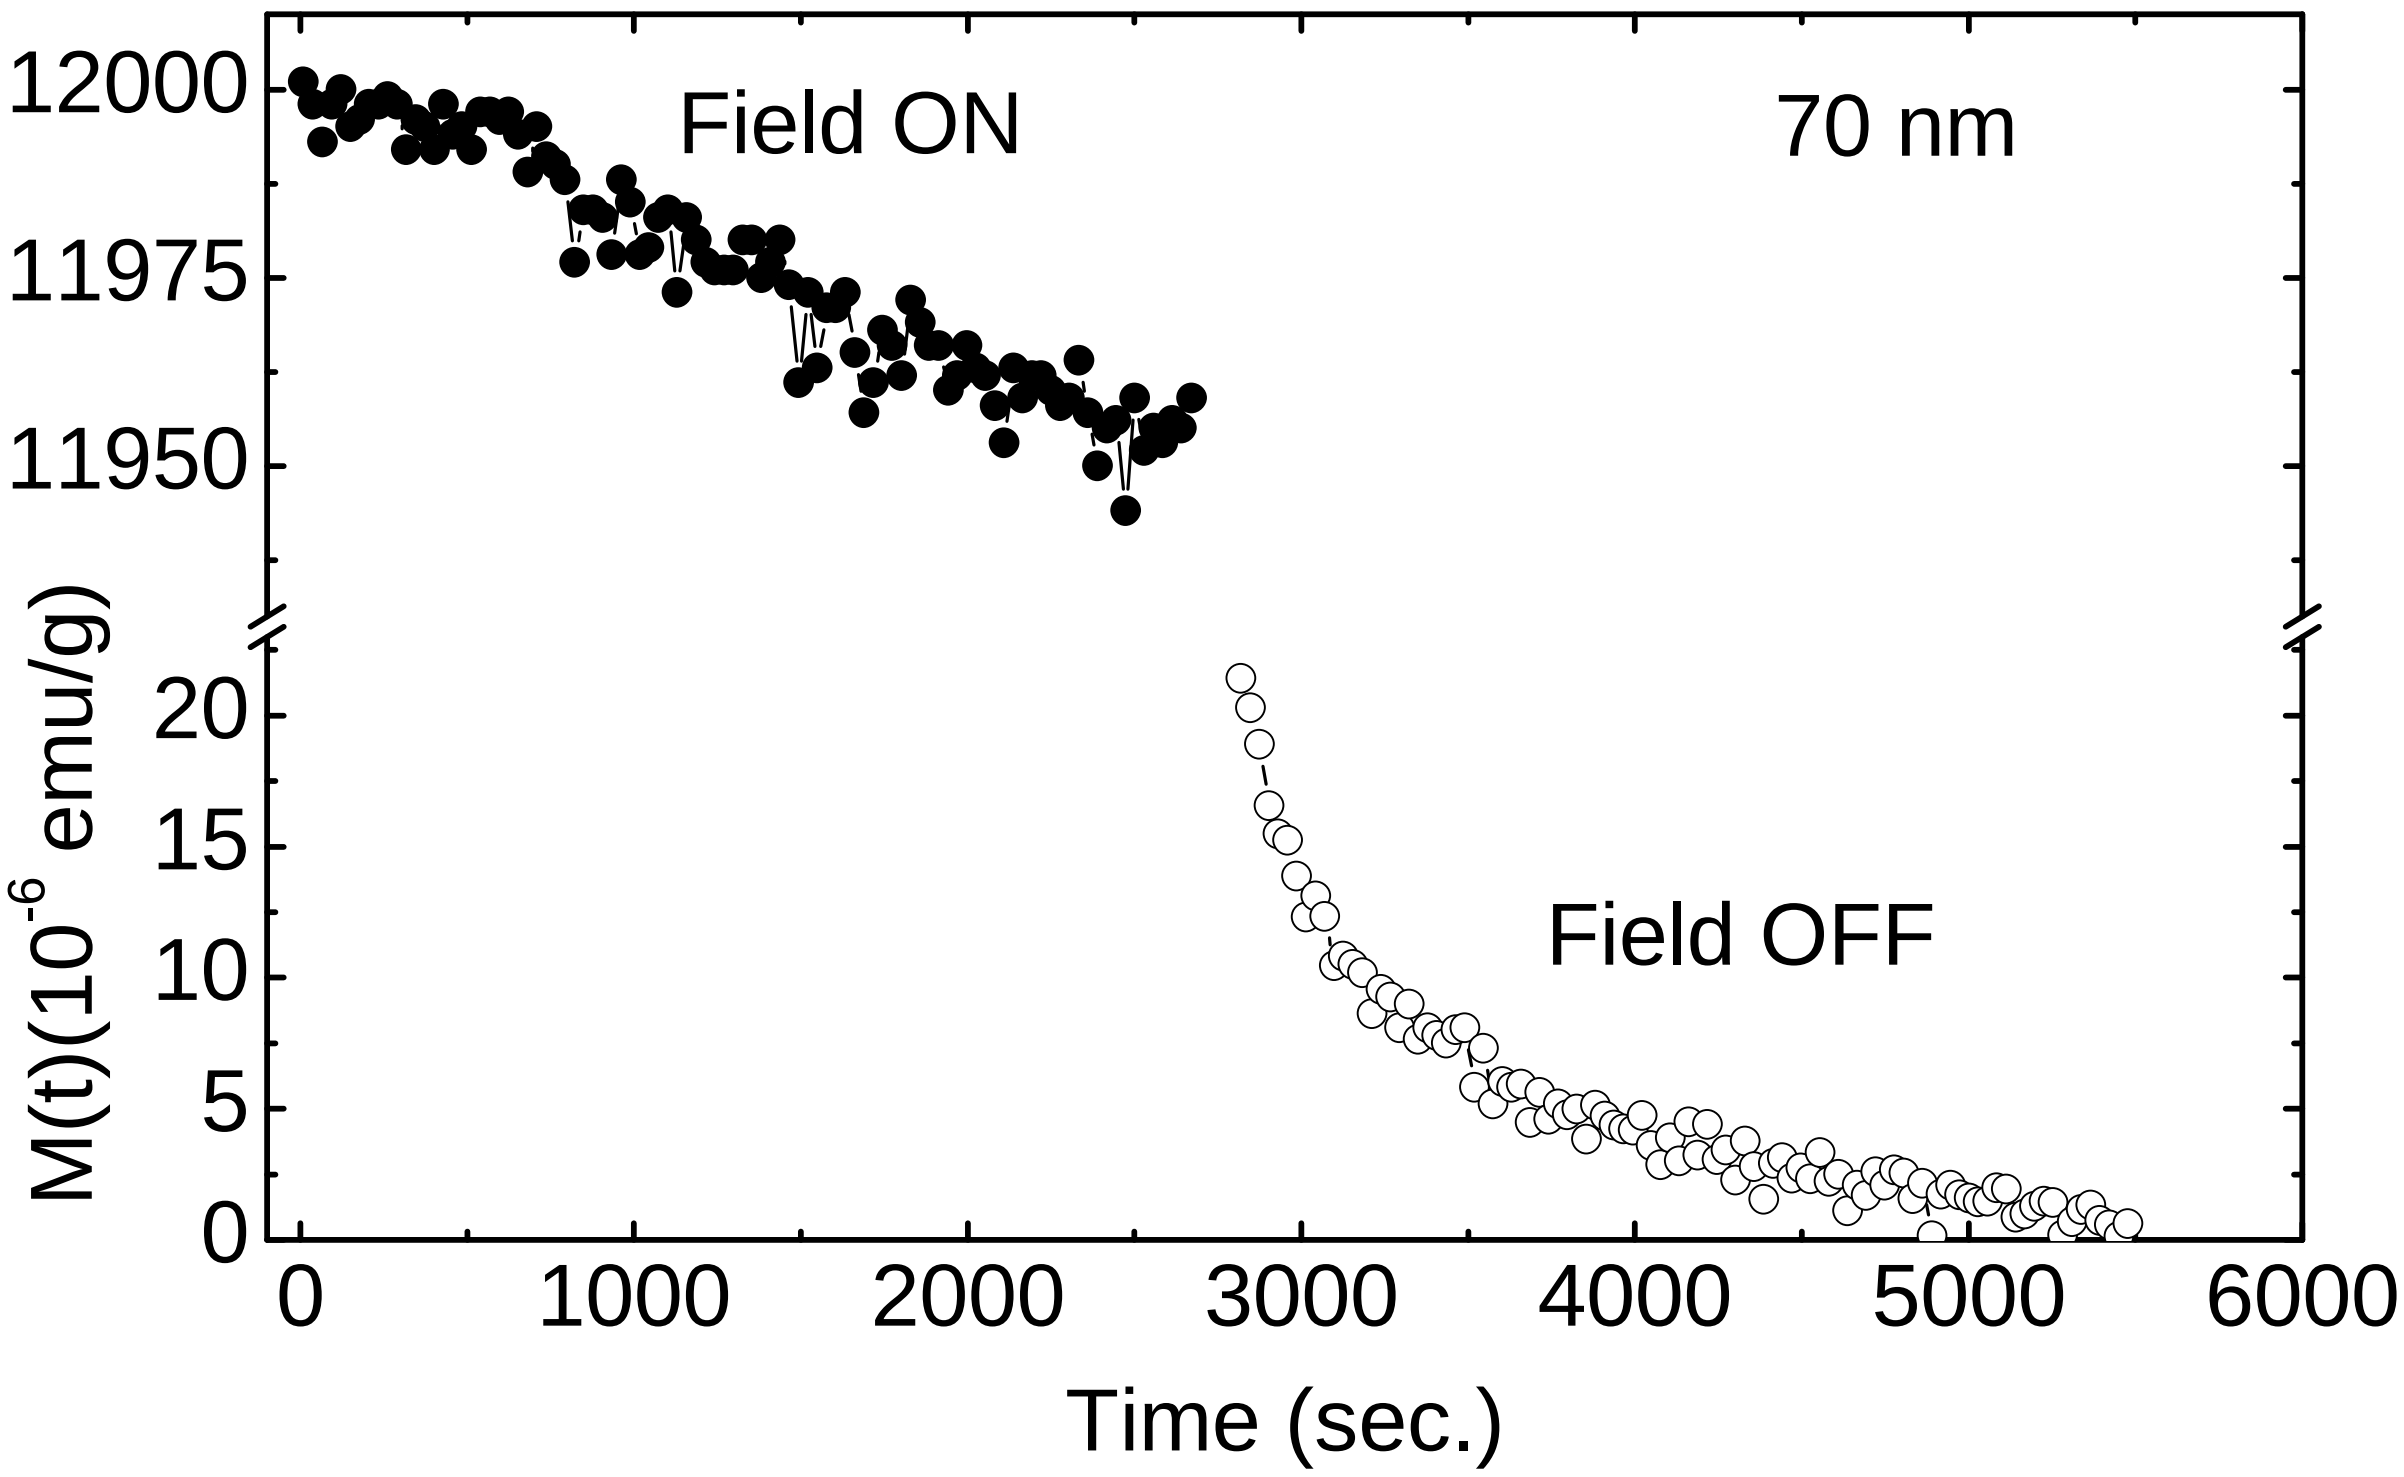

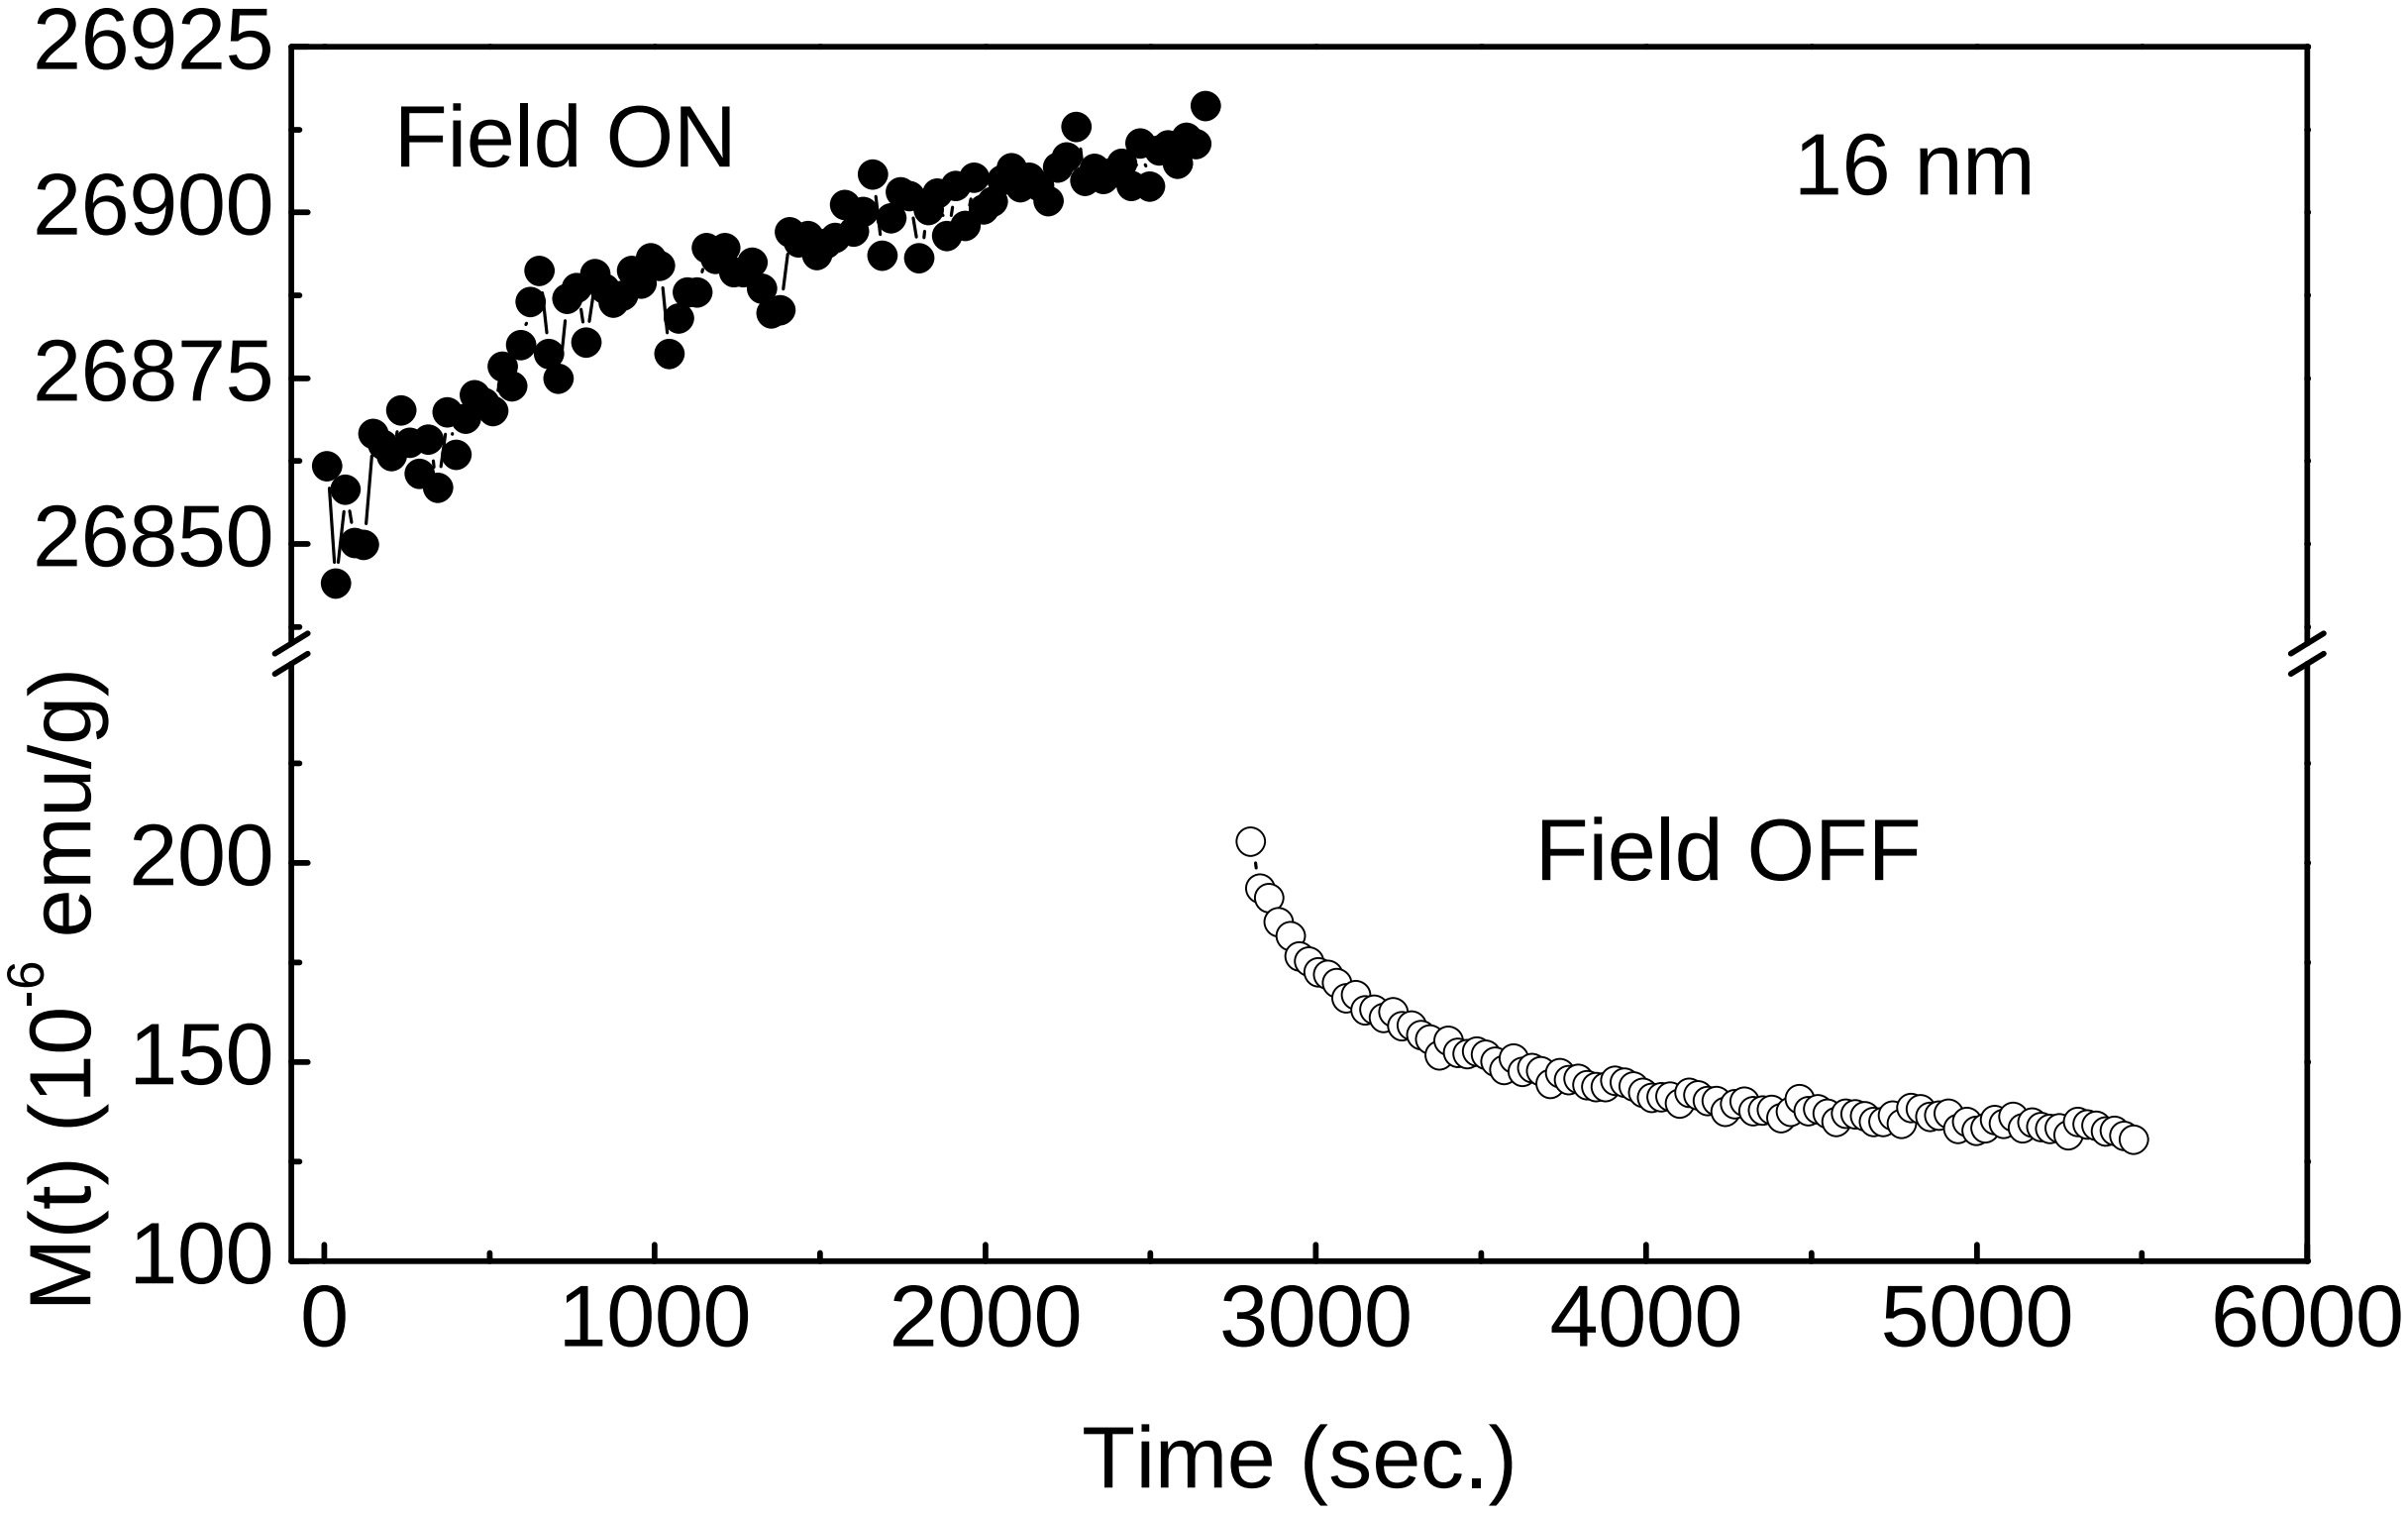

Fig 1. M(t) data for two selected samples. Each sample is zero field cooled to 2 K and waited for 100 seconds before applying 100 Oe magnetic field. Relaxation is observed in presence (ON state) and absence (OFF state) of field.

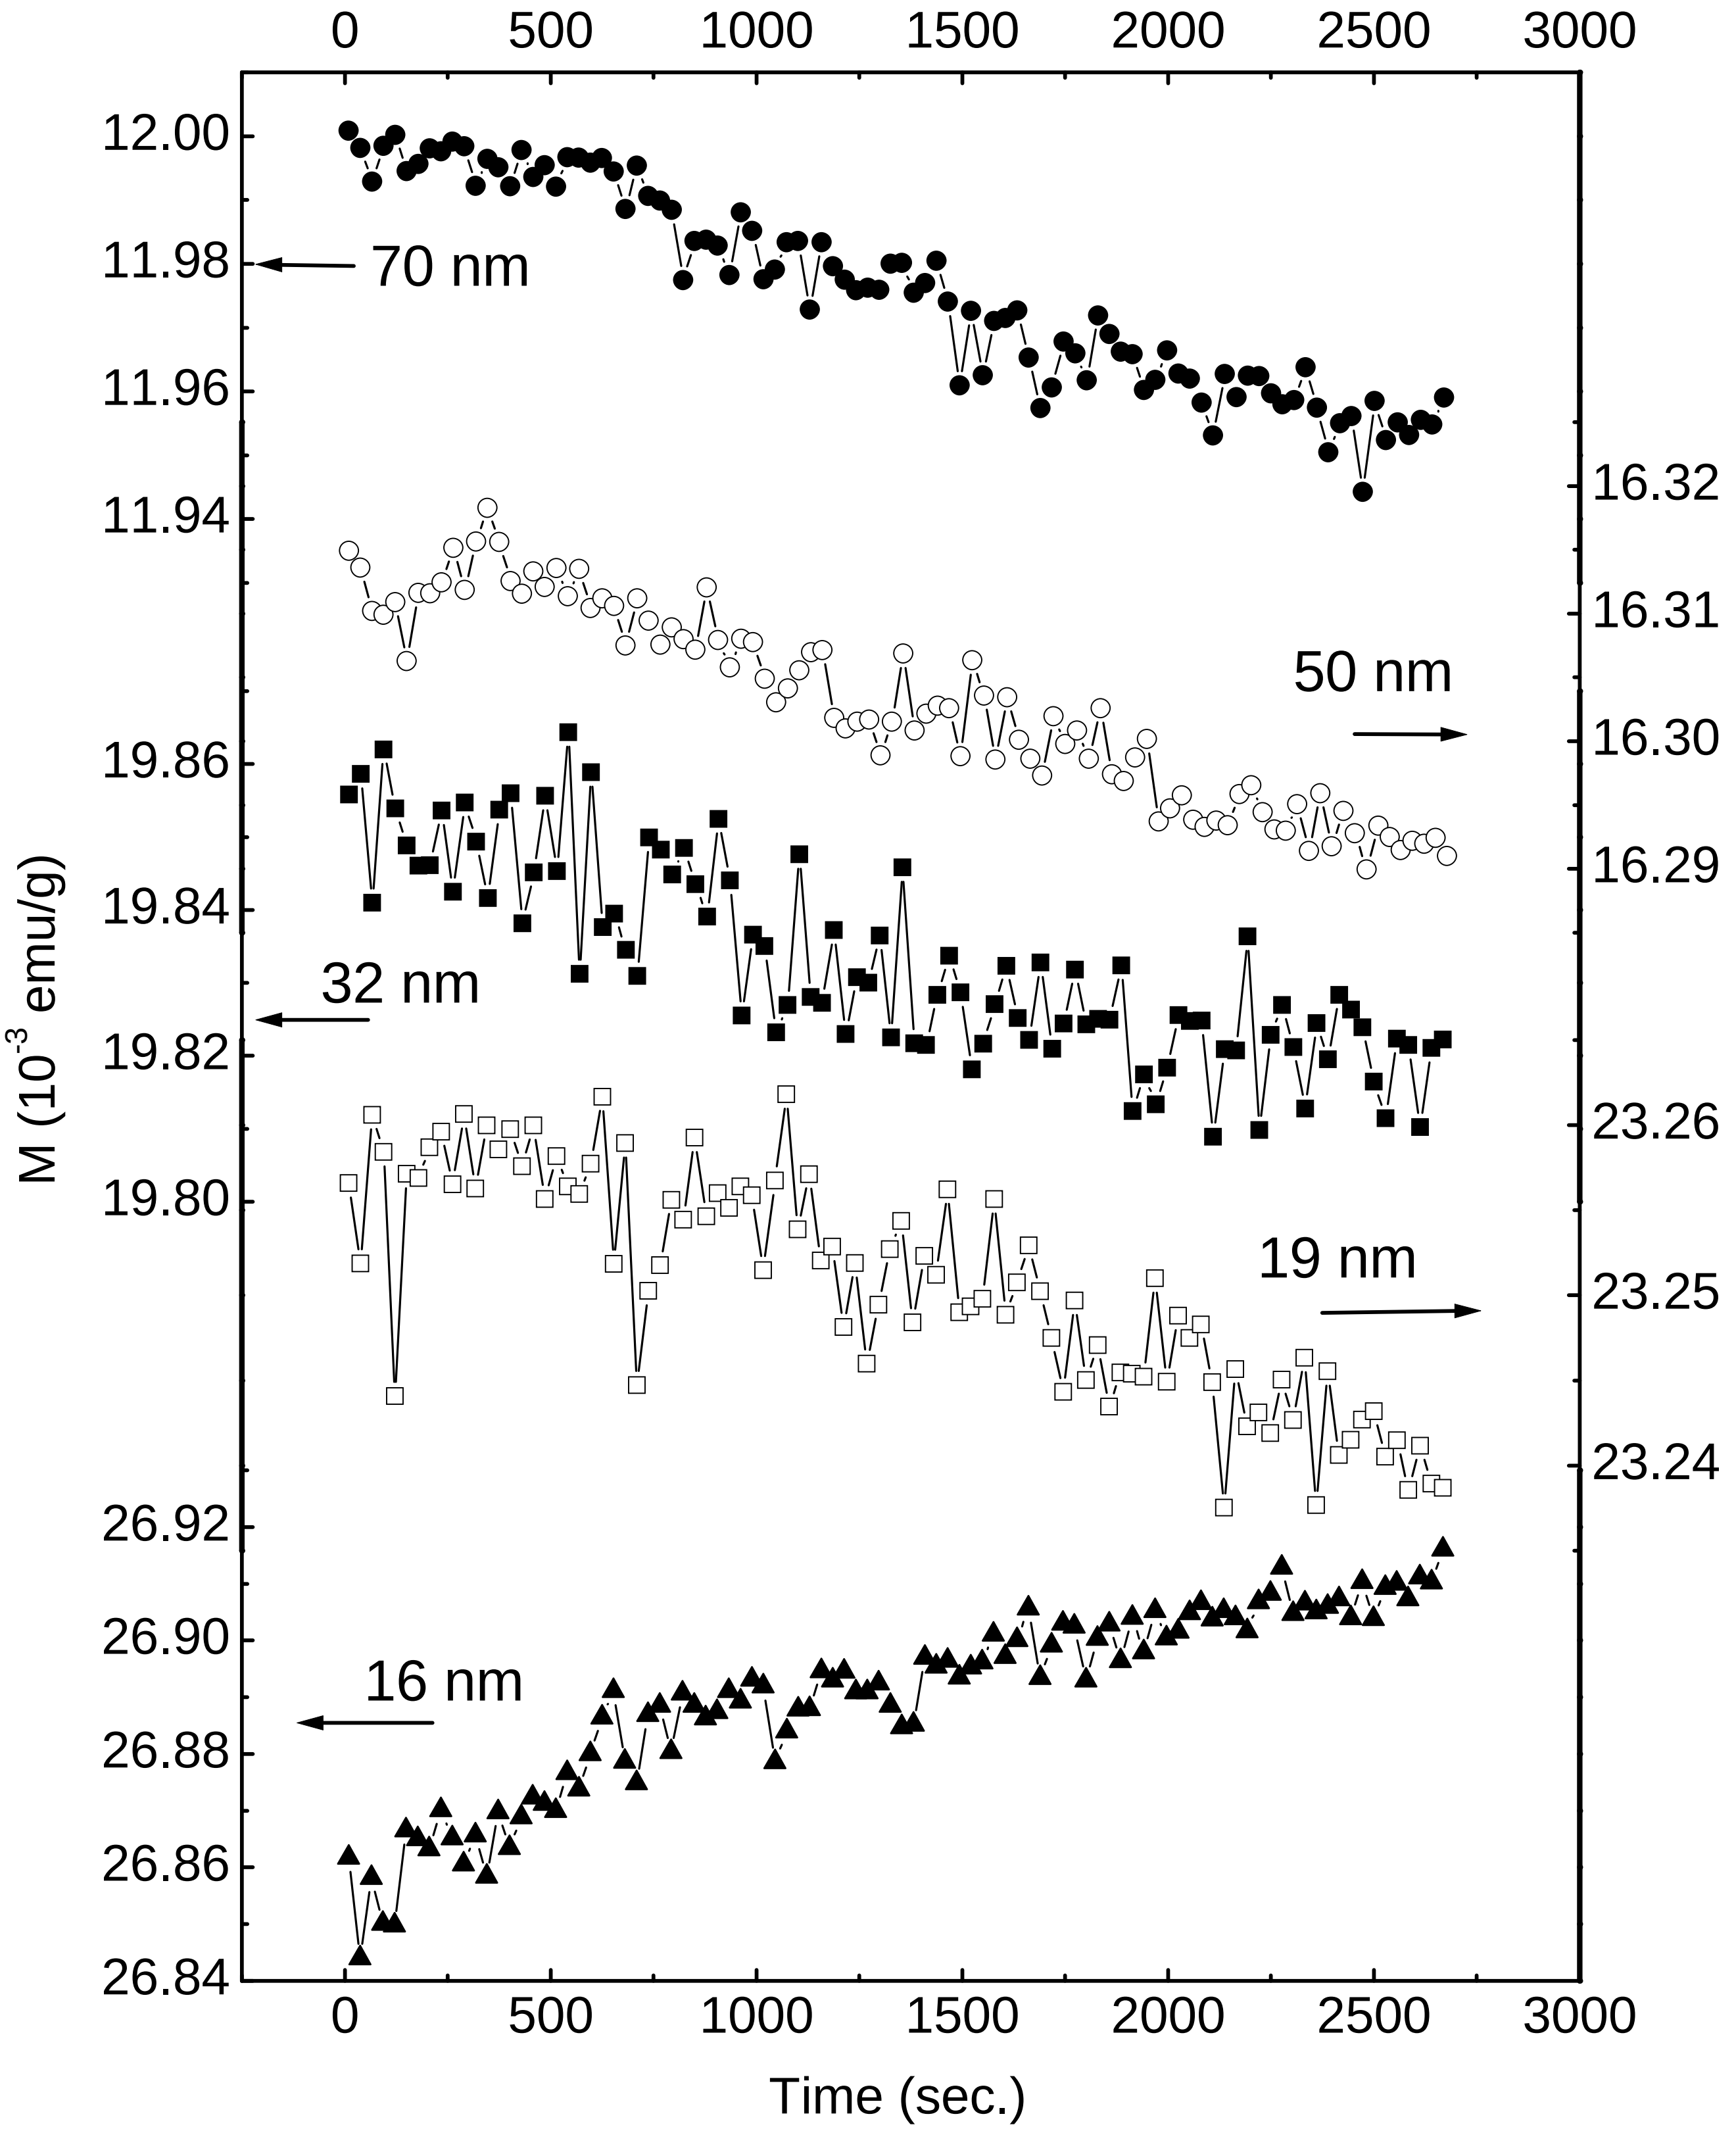

Fig. 2 Relaxation of zero field cooled magnetization (M(t)) for different $CoRh_2O_4$ nanoparticles in the presence of 100 Oe (ON state) at 2 K after waiting time 100 s. Arrows indicate the magnetization axis of the corresponding sample

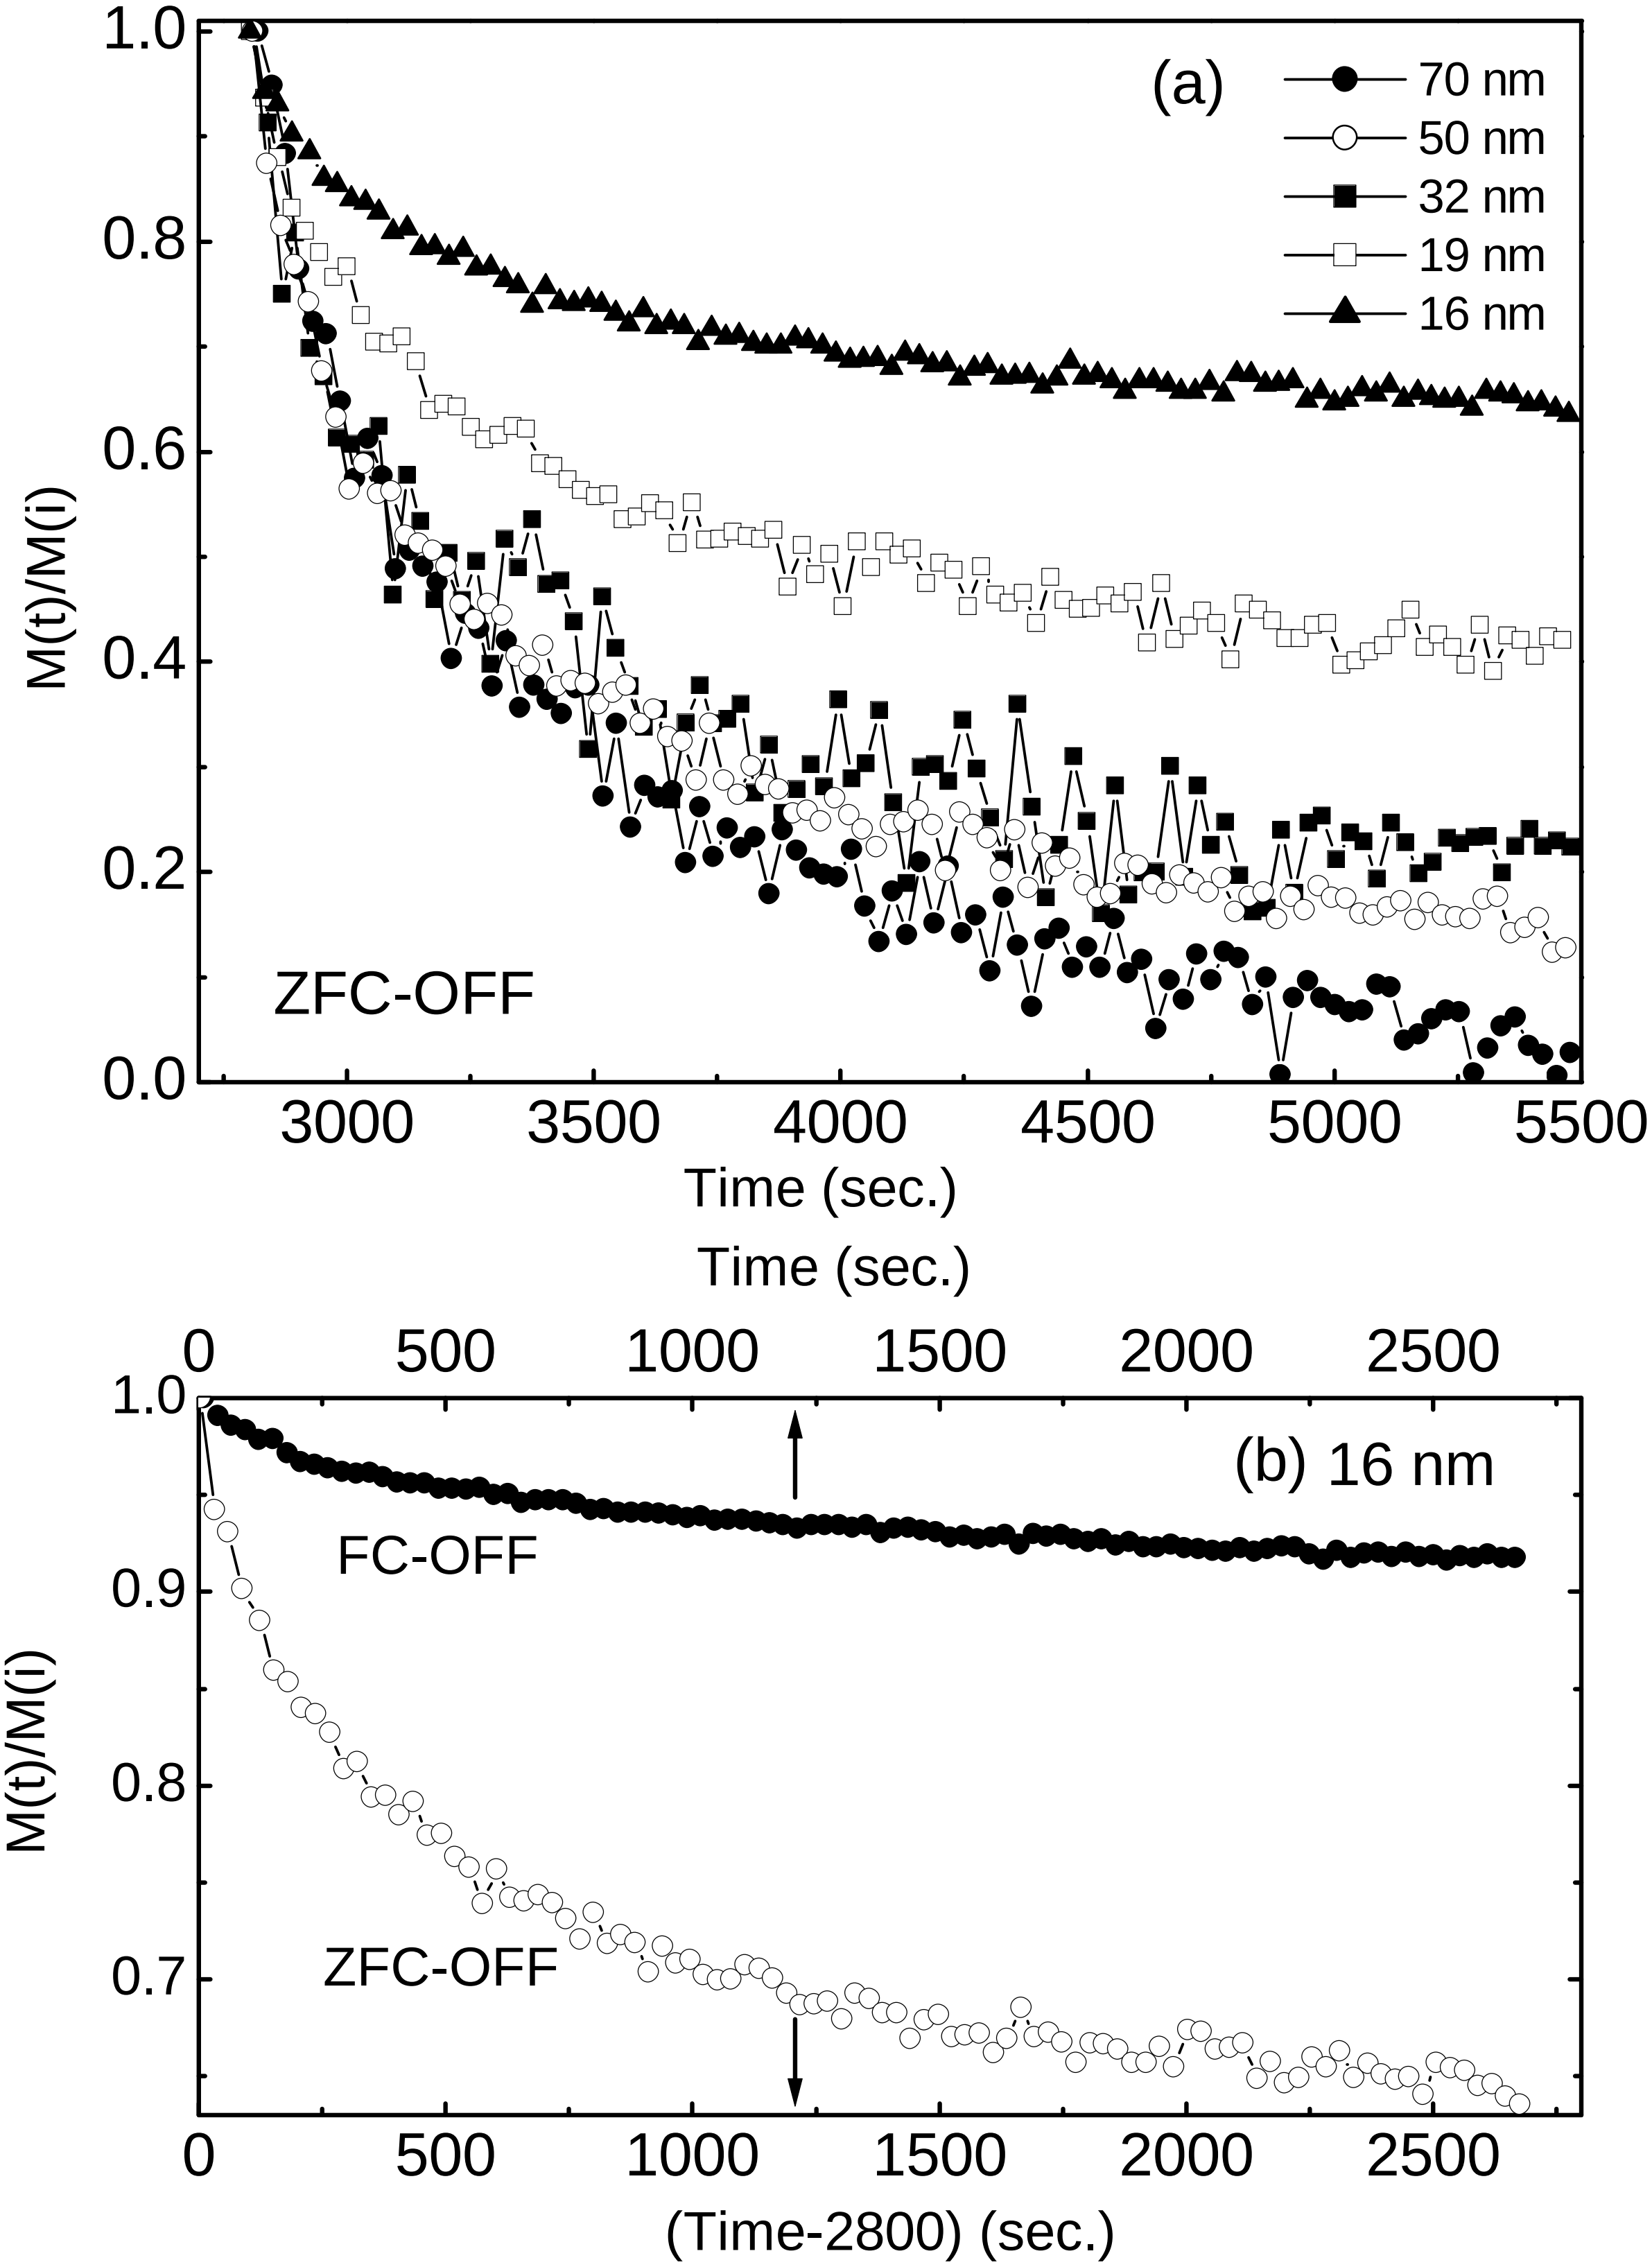

Fig. 3 (a) M(t) data for different $CoRh_2O_4$ nanoparticles in ZFC-OFF state at 2 K. (b) Comparative M(t) data for FC-OFF and ZFC-OFF states at 2 K for 16 nm samples. M(t) data are normalized by the first point M(i), where i = 10 sec. and 2800 sec. for FC and ZFC, respectively. Also note the modified time scale only for ZFC-OFF state in Fig. 3b.

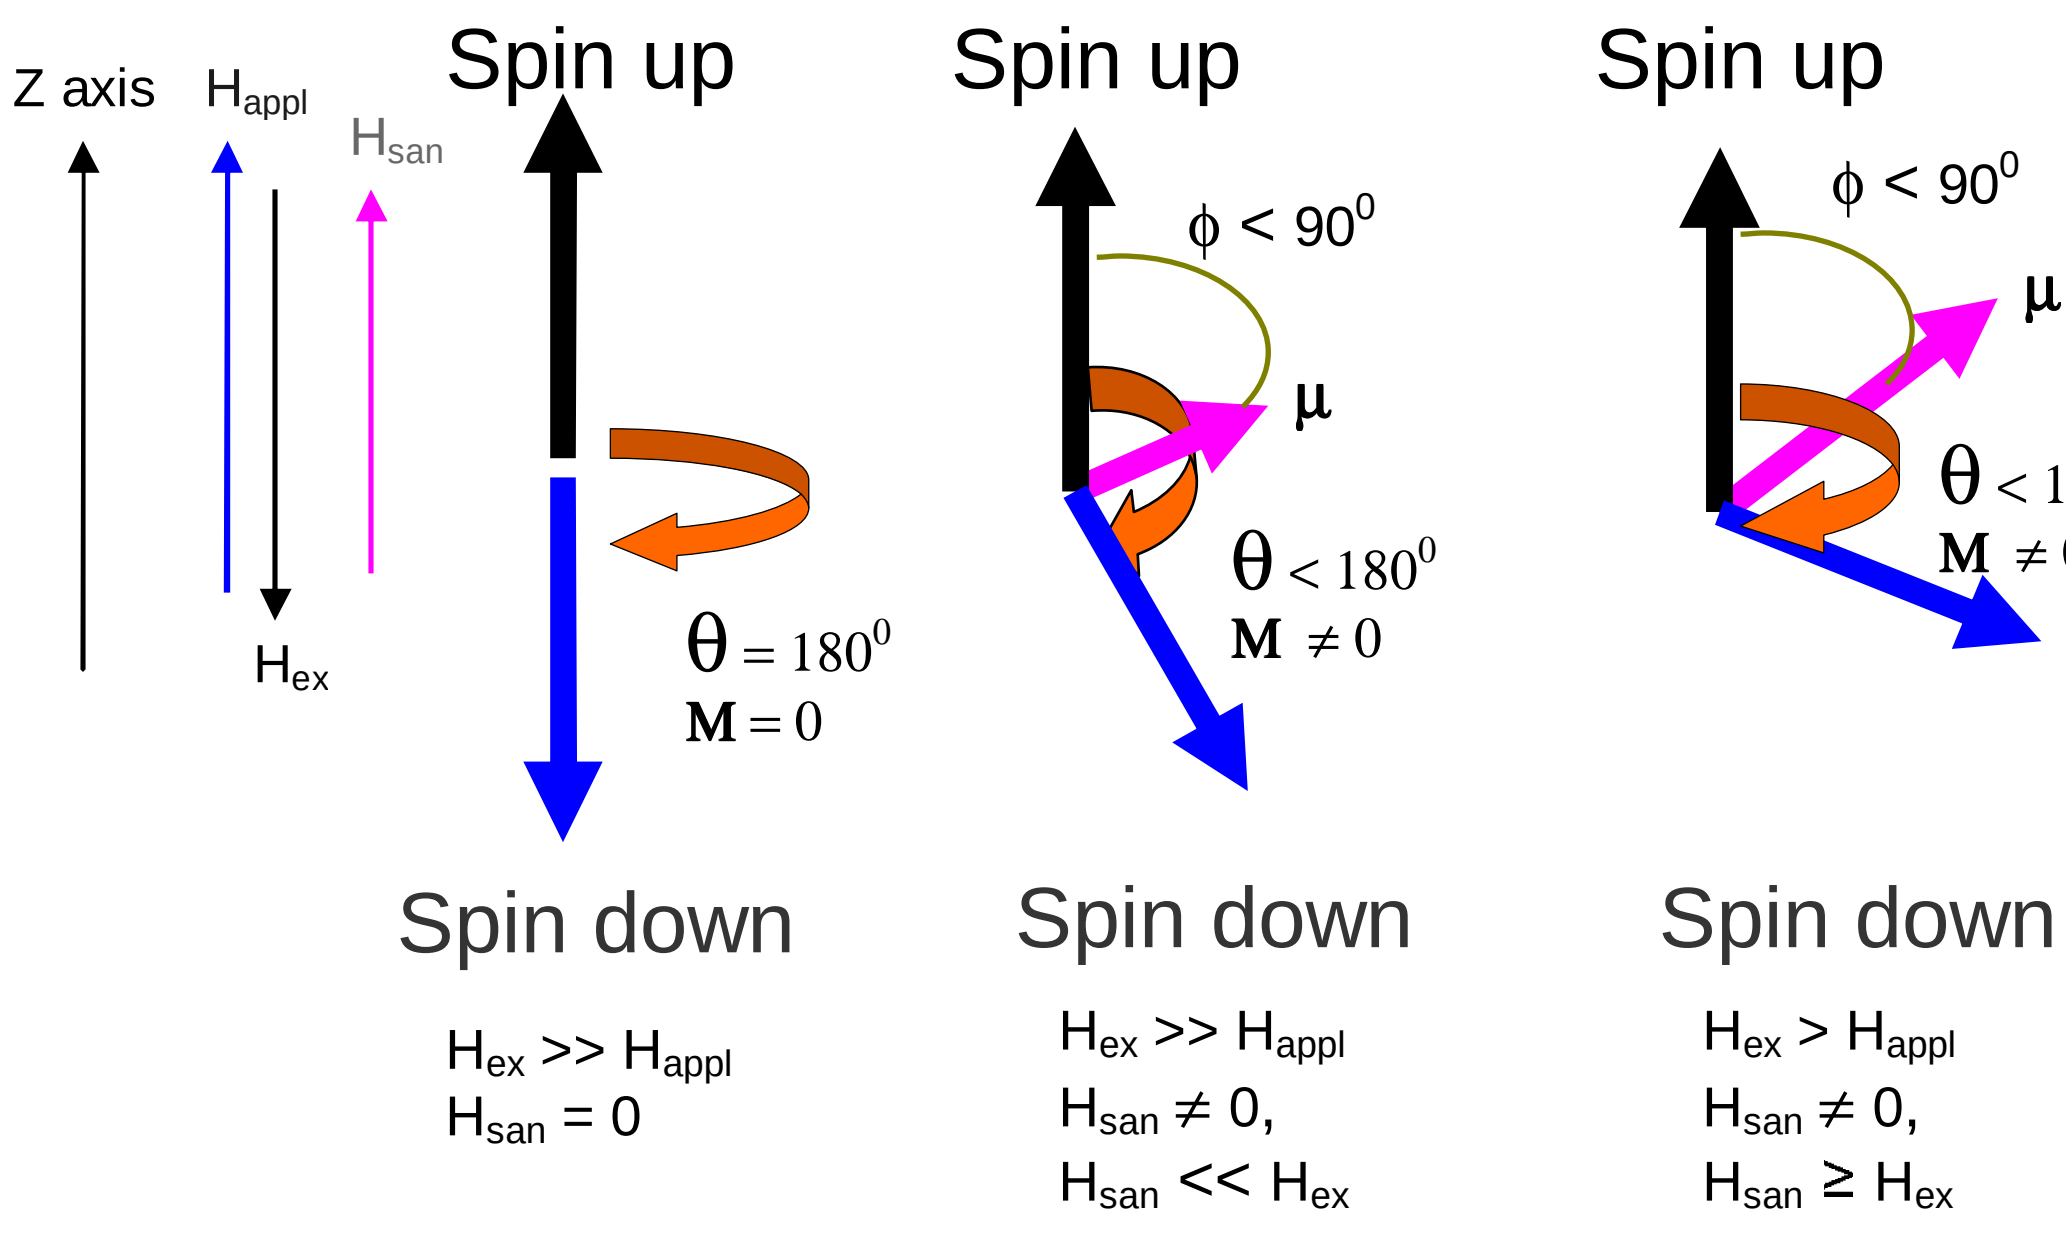

(a) bulk (b) small nps © smaller nps

Fig. 4 (Colour online) A schematic diagram to show competition in shell-shell and core-shell interfaces between antiferromagnetic exchange interactions (H_{ex}) and surface exchange anisotropy field (H_{san}) in presence of applied magnetic field (H_{appl}) along + z axis (spin up direction) for bulk and nanoparticle samples (nps). We have assumed that (H_{ex}) is along – z axis, effective H_{san} along + z axis. Magnetization (M) is defined as the average moment along + z axis, i.e. $M = \langle\mu\rangle_{Z.}$